

Elastic forces that do no work and the dynamics of fast cracks

Fernando Lund
 Departamento de Física
 Facultad de Ciencias Físicas y Matemáticas
 Universidad de Chile
 Casilla 487-3, Santiago, Chile

Abstract

Elastic singularities such as crack tips, when in motion through a medium that is itself vibrating, are subject to forces orthogonal to the direction of motion and thus impossible to determine by energy considerations alone. This fact is used to propose a universal scenario, in which three dimensionality is essential, for the dynamic instability of fast cracks in thin brittle materials.

The dynamics of crack tips is of particular relevance to the fracture of materials[1] and to earthquake rupture[2]. In addition, recent improvements in instrumentation techniques have revealed unstable crack dynamic behaviour reminiscent of what is observed in other physical systems driven far from equilibrium[3, 4, 5, 6]. These experiments have taken a close quantitative look at the crack-tip velocity fluctuations, ultrasound emission and surface heterogeneities in glass and plexiglass associated with long standing puzzles in the tensile cracking of very brittle solids[7].

The theoretical effort directed at an understanding of these phenomena has been largely based on two dimensional modelling. It includes analysis based on a continuum approach that considers a cohesive region at the crack tip[8] and numerical computations using lattice[9] as well as molecular dynamics[10] techniques. However, ultrasound[4, 5], surface topography[3, 5] and velocity fluctuation[3, 5] measurements clearly involve length scales comparable or smaller than sample thickness, strongly suggesting that three dimensionality cannot be

ignored. The possible relevance of results obtained in a study of the three dimensional propagation of a crack within an heterogeneous model elastic solid have been recently pointed out[11].

The purpose of this paper is to point out that, when the motion of an elastic singularity deviates from a straight line, energy balance considerations are insufficient to determine the singularity's motion since (in two dimensions) they provide only one equation to determine the dynamics of two degrees of freedom. Thus, in addition, the equation of momentum balance must be considered. In so doing there results a new elastic force that does no work[12] and that consequently cannot be obtained on the basis of energy considerations alone. For a crack moving in a thin elastic plate, consideration of three dimensionality makes this force operative and provides a scenario, some of it qualitative, some of it quantitative, that appears to explain many of the observed experimental facts.

The equations of dynamic elasticity in a medium of dimensionality d and density ρ can be obtained as extrema of the action functional

$$S = \frac{1}{2} \int dt d^d x (\rho \dot{u}^2 - \sigma_{ij} s_{ij}) \quad (1)$$

where σ_{ij} is the stress, s_{ij} the strain, $i, j = 1, \dots, d$ and $\vec{u}(\vec{x}, t)$ the particle deviation at time t from an equilibrium position $\vec{x}$. When stress and strain are linearly related, $\sigma_{ij} = c_{ijkl} s_{kl}$, the well known linear equations can be written in conservation-law form[13, 14]:

$$\frac{\partial T^{00}}{\partial t} + \frac{\partial T^{0i}}{\partial x^i} = 0 \quad (2)$$

$$\frac{\partial T^{j0}}{\partial t} + \frac{\partial T^{ji}}{\partial x^j} = 0, \quad (3)$$

with

$$T^{00} = \frac{\rho}{2} \left(\frac{\partial u}{\partial t} \right)^2 + \frac{1}{2} c_{ijkl} \frac{\partial u^i}{\partial x^j} \frac{\partial u^k}{\partial x^l} \quad (4)$$

$$T^{0j} = -c_{jikl} \frac{\partial u^i}{\partial t} \frac{\partial u^k}{\partial x^l} \quad (5)$$

$$T^{j0} = -\rho \frac{\partial u^i}{\partial t} \frac{\partial u^i}{\partial x^j} \quad (6)$$

$$T^{ji} = c_{klmi} \frac{\partial u^k}{\partial x^l} \frac{\partial u^m}{\partial x^j} + \frac{1}{2} \left(\rho \left(\frac{\partial u}{\partial t} \right)^2 - c_{klmn} \frac{\partial u^k}{\partial x^l} \frac{\partial u^m}{\partial x^n} \right) \delta_{ji} \quad (7)$$

The components of the energy momentum tensor T have the following interpretation: T^{00} is the energy density, T^{0j} is the energy flux, T^{j0} is the momentum density and T^{ji} is the momentum flux.

If Eqns. (2) are integrated over a volume $\mathcal{V}$ that is bounded by a surface $\mathcal{S}$ that is possibly moving with velocity $\vec{V}$ one obtains energy conservation

$$\frac{d}{dt} \int_{\mathcal{V}} d^d x T^{00} = \int_{\mathcal{S}} dS_j T^{0j} - \int_{\mathcal{S}} dS_j V^j T^{00} \quad (8)$$

and (linear) momentum conservation

$$\frac{d}{dt} \int_{\mathcal{V}} d^d x T^{i0} = \int_{\mathcal{S}} dS_j T^{ij} - \int_{\mathcal{S}} dS_j V^j T^{i0}. \quad (9)$$

If Eqn. (8) is applied to the case of a crack advancing in a straight line, we get the usual equation of motion for the crack tip[1]. There is energy flow into the tip, which is equated to the surface energy that is created as the crack advances. The volume $\mathcal{V}$ is the volume of the whole sample, and the surface $\mathcal{S}$ is composed of a small (i.e. smaller than any relevant length such as sample thickness or radiation wavelength) cylinder surrounding the crack tip, the lips of the crack, and the boundaries of the sample. The contribution of the small cylinder around the tip is finite because stresses behave like $1/\sqrt{r}$, with r distance to the tip, near the crack. The crack lips do not contribute because they are at rest and, by definition, they are traction free. Remote surfaces do not contribute as long as radiation reaction is neglected.

It is a simple matter to check that, for a crack advancing along the x^1 direction at velocity V the following is true:

$$V \frac{dP^1}{dt} = \frac{dE}{dt} \quad (10)$$

where

$$E = \int_{\mathcal{V}} d^d x T^{00} \quad (11)$$

$$P^i = \int_{\mathcal{V}} d^d x T^{i0} \quad (12)$$

so that the momentum equation and the energy equation provide the same information. Now, if the crack tip motion is not constrained to a straight line, the momentum equations provide the additional information needed to determine the motion. In two dimensions, one equation would not suffice and less so in three.

Consider now the normal modes of vibration of an elastic plate in three dimensions[15]. For a thin plate of thickness h there are, to leading order, one

dilatational mode with frequencies $n\pi\alpha/h$ and two shear modes with frequencies $n\pi\beta/h$, where α is the speed of sound and β the speed of shear waves, both in bulk, and $n = 1, 2, 3, \dots$ (Figure 1). When a crack propagates along the x^1 direction, say, because of static loading along x^3 , the modes involving motions parallel to the crack faces will be unaffected. There is, however, one shear mode that involves motion along the x^3 direction that will be incompatible with the traction-free boundary condition that defines a crack. Consequently this mode will be modified by the presence of the crack and stress concentration, in addition to the one already present due to the static loading, will result. The question naturally arises as to how this new stress concentration at the crack tip will affect its dynamics. Of course, these vibrating modes do not exist in two dimensions.

In order to give a quantitative assesment of this effect we consider the crack surface near the tip as a continuous distribution of infinitesimally small dislocations. These dislocations are defects in a continuum, and they are not related to a (possibly non-existent) underlying crystal structure. That this makes sense is well-known in the static case[16] and has also been used in dynamics, to show that a crack may, under certain circumstances, acquire inertia[17]. The basic idea is that the infinitesimal dislocations arrange themselves so as to negate the externally applied stress and enforce the no traction boundary condition at the crack surface. The exact functional behaviour of the crack opening displacement that will result in the case at hand is not needed at the current stage of development of the theory, although it presents itself as an attractive challenge for future research. We only need to know that *some* such distribution exists.

Consider then an edge dislocation of (infinitesimal) Burgers vector $\vec{b}$ moving with velocity $\vec{V}$ in an elastic medium whose (small) particle displacements away from an equilibrium position are $\vec{U}(\vec{x}, t)$. The relative orientation of $\vec{b}$ and $\vec{V}$ is immaterial. The time dependence of $\vec{U}$ does *not* include a possible motion of the body as a whole, since that would not be a small deviation away from an equilibrium position. The dislocation generates around it a well known[18] particle displacement $\vec{u}(\vec{x}, t)$ in which strain and particle velocity are related, at short distances, by ($a, c = 1, 3$)

$$\frac{\partial u_a}{\partial t} = V_c \frac{\partial u_a}{\partial x^c} \quad (13)$$

The point is to compute the force

$$F^j \equiv \frac{dP^j}{dt} \quad (14)$$

given by (9) and (12), for which the relevant integrals have to be evaluated around a small circle enclosing the dislocation. Assuming the medium to be linear down

to this small circle, the particle displacements will be the sum

$$\vec{u} + \vec{U} \quad (15)$$

of dislocation generated plus externally imposed ones. Since the components of the energy momentum tensor T are bilinear functions of derivatives of displacements, they will decompose naturally in three terms: one involving only $\vec{u}$, one involving only $\vec{U}$, and one involving both $\vec{u}$ and $\vec{U}$ which is the only one of interest:

$$T^{j0} = -\rho \left(\frac{\partial u^i}{\partial t} \frac{\partial U^i}{\partial x^j} + \frac{\partial U^i}{\partial t} \frac{\partial u^i}{\partial x^j} \right) \quad (16)$$

and similarly for T^{ij} . Substitution of the field $\vec{u}$ for an edge dislocation[18] into (9), (12) and (14) using (16) gives the result

$$F^j = F_{PK}^j + F_V^j \quad (17)$$

where

$$F_{PK}^j = b_i \Sigma_{ij} \epsilon_{jkm} \hat{t}_m \quad (18)$$

with $\hat{t}$ the unit vector along the dislocation line and $\Sigma_{ij} = c_{ijkl} \partial U_k / \partial x_m$ the external stress, is the usual Peach-Koehler force. In addition there is a force[19]

$$F_V^j = \rho \epsilon_{jkm} V_k \hat{t}_m b_i \dot{U}_i \quad (19)$$

that acts only if the dislocation is moving ($\vec{V} \neq 0$), if the elastic medium itself is also independently moving ($\dot{\vec{U}} \neq 0$), and is perpendicular to the direction of motion and consequently does no work. For a Burgers vector corresponding to a mode-I crack, the static loading gives a Peach-Koehler force along the cleavage plane. When summed over the many infinitesimal dislocations that make up the crack tip, it gives the usual work-performing force that is considered in the standard treatment of crack-tip dynamics. It does not have a component perpendicular to the motion. The vibrational modes of the plate that have been previously considered give a vanishing Peach-Koehler force. The force $\vec{F}_V$, on the other hand, is nonvanishing only for the shear mode that was already argued to be concentrated at the tip in order to satisfy the proper boundary conditions along the crack faces. The static loading of course does not contribute to it.

As it was mentioned at the beginning of this communication, recent experiments [3, 4, 5, 6] indicate that cracks in glass and plexiglass suffer an instability at a critical velocity, beyond which there are strong sound emissions, strong velocity fluctuations, and strong surface heterogeneities. The limiting velocity is well below the theoretically expected Rayleigh wave velocity. We are now in a position to propose the following scenario to explain those observations:

1. The crack starts propagating, and right away it starts emitting elastic (both longitudinal and shear) radiation. The pull tabs possibly also radiate at the beginning. The crack accelerates.
2. Normal modes (in thickness) of vibration of the plate are established, and they are responsible for a new oscillating force that does no work on the crack and is proportional to the tip's velocity. The fundamental mode will dominate but at sufficiently high crack velocity the forcing may be enough to also excite higher modes. To leading order they are the modes of an infinitely extended slab. Next order corrections should take into account the finite size and shape of the sample.
3. The crack responds by oscillating to the tune of this new periodic (possibly, multiply periodic) forcing and, hence, emitting radiation (both shear and longitudinal) primarily at the same frequencies it is being forced. This radiation reinforces the normal modes that, in turn, feed back on the tip. This is the instability.
4. In a non-amorphous material such as a crystal, the surface energy may be higher for out of plane crack motions and thus this mechanism may be non operative.
5. Terminal speed (i.e. average speed along line of propagation) is determined by energy spent by external stress. Since the crack path is effectively increased, the average speed of advance is decreased.

The above scenario is universal in the sense that it applies to any brittle material that is described by linear elasticity. At this stage, there is no calculation of a transition velocity, but a reasoning that indicates why there should be an instability as the crack velocity increases. There is, however, a clear consequence that sound radiation, velocity oscillations and surface roughness are different manifestations of the same phenomenon, whose spectra should be peaked at the normal modes of the elastic plate. These consequences should be amenable to experimental verification, for example by studying the effect of sample thickness and of sample ensonification.

To conclude: it has been established that elastic singularities are subject to velocity dependent forces that do no work. On this basis, a scenario has been proposed to explain recent observations of dynamic crack instabilities. The proposed scenario includes the three dimensionality of the problem as an essential ingredient. It provides a qualitative physical origin for the instability, and a quantitative prediction for the frequencies that should be notorious in the resulting spectra of

sound, surface and velocity fluctuations, namely, the eigenfrequencies of the thin plate that is being fractured.

Stimulating discussions with S. Ciliberto are gratefully acknowledged. Part of this research was done while on a visit to the Centre Emile Borel, wherein a fruitful conversation with M. Benamar was held. This work was supported by Fondecyt Grant 1940429, CCE Contract CI1*CT91-0947 and the Andes Foundation.


References

- [1] L. B. Freund, *Dynamic Fracture Mechanics*, Cambridge U.P. (1990).
- [2] B. V. Kostrov and S. Das, *Principles of Earthquake Source Mechanics*, Cambridge U.P. (1988).
- [3] J. Fineberg et. al., *Phys. Rev. B* **45**, 5146 (1992); *Phys. Rev. Lett.* **67**, 457 (1991).
- [4] S. P. Gross et. al., *Phys. Rev. Lett.* **71**, 3162 (1993).
- [5] J. F. Boudet, S. Ciliberto and V. Steinberg, *Europhys. Lett.* **30**, 337 (1995).
- [6] E. Sharon, S. P. Gross and J. Fineberg, *Phys. Rev. Lett.* **xx**, xxx (1995).
- [7] W. G. Knauss and K. Ravi-Chandar, *Int. J. Fract.* **27**, 127 (1985).
- [8] E. Ching, *Phys. Rev. E* **49**, 3382 (1994); K. Runde, *Phys. Rev. E* **49**, 2597 (1994); J. S. Langer and H. Nakanishi, *Phys. Rev. E* **48**, 439 (1993); J. S. Langer, *Phys. Rev. A* **46**, 3123 (1992).
- [9] M. Marder and S. Gross, “Origin of Crack Instabilities”, submitted to *J. Mech. Phys. Solids*; M. Marder and X. Liu, *Phys. Rev. Lett.* **71**, 2417 (1993).
- [10] F. F. Abraham et. al., *Phys. Rev. Lett.* **73**, 272 (1994).
- [11] J. R. Rice, Y. Ben-Zion and K.-S. Kim, *J. Mech. Phys. Solids*, **42**, 813 (1994).
- [12] In a different physical context, an example of such a force is that exerted by a magnetic field on a moving electric charge.
- [13] J. P. Eshelby, *Phil. Trans. R. Soc. Lond.* **A244**, 87 (1951). See B. A. Bilby, in “Fundamentals of Deformation and Fracture”, ed. by B. A. Bilby, K. J. Miller and J. R. Willis, Cambridge U. P. (1985) for a historical account of Eshelby’s many contributions.


- [14] F. Lund, *J. Mater. Res.* **2**, 280 (1988).
- [15] J. D. Achenbach, *Wave propagation in elastic solids*, North Holland, (1984).
- [16] E. Smith, “Dislocations and cracks”, in *Dislocations in solids*, Vol. 4, ed. by F. R. N. Nabarro, North-Holland, (1979); B. A. Bilby and J. D. Eshelby, in *Fracture*, Vol. 1, Ed. by H. Liebowitz, Academic Press, (1969).
- [17] M. Díaz and F. Lund, *Philos. Mag.* **A 60**, 139 (1989).
- [18] J. P. Hirth and J. Lothe, *Theory of dislocations*, second edition, Wiley, (1982).
- [19] An alternative derivation of this result can be found in [14]. For a screw dislocation, the existence of a velocity dependent force was guessed by J. P. Eshelby, *Phys. Rev.* **30**, 248 (1953) on the basis of an analogy with lines of constant electric charge. See also F. Lund, *Phys. Rev. Lett.* **54**, 14 (1985).

Caption for figure


Figure 1 A thin elastic plate of thickness h has, to leading approximation, three normal modes of elastic oscillation: one (a) is dilatational, with eigenfrequencies $n\pi\alpha/h$ and two (b-c) are shear, with eigenfrequencies $n\pi\beta/h$, where α is the speed of sound, β is the speed of shear waves, and $n = 1, 2, \dots$. When a crack propagates along the x^1 direction, for instance because of static loading along x^3 , the shear mode indicated in (c) is incompatible with traction-free boundary conditions along the crack faces, leading to a new stress concentration at the tip that will modify the crack dynamics.

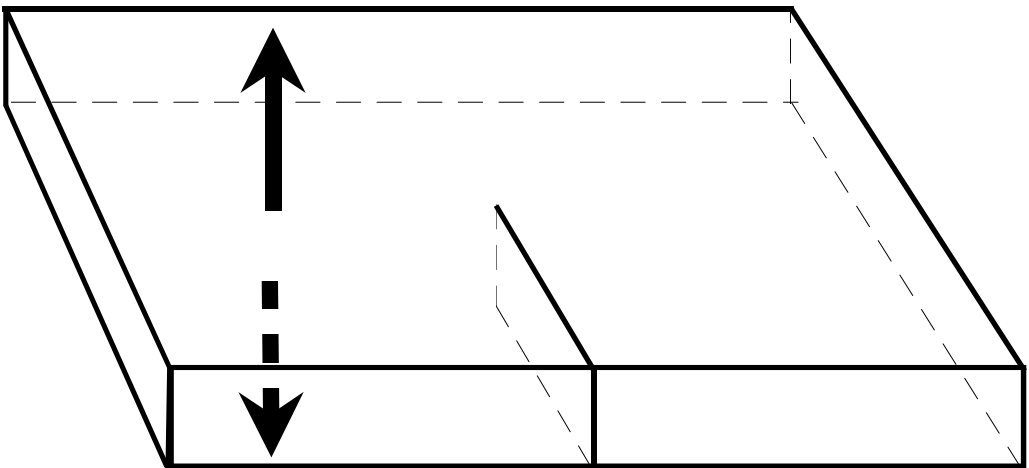

(a)

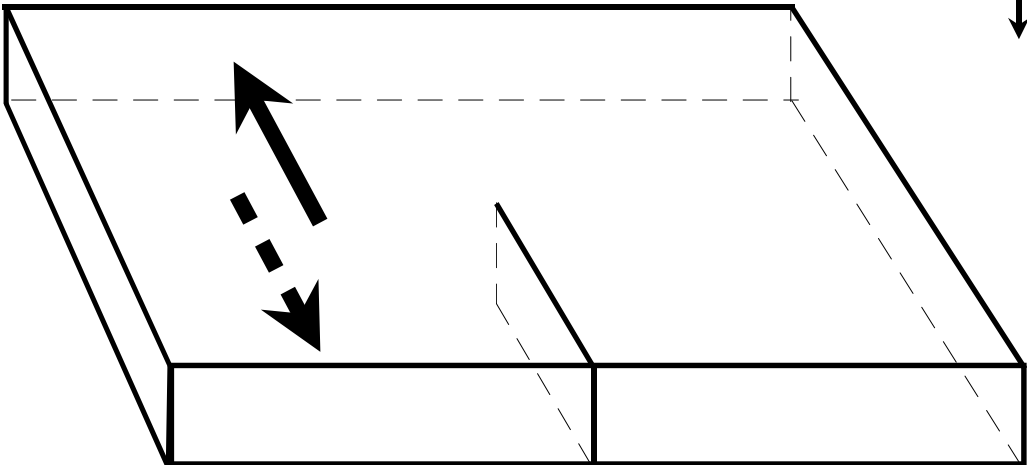

(b)

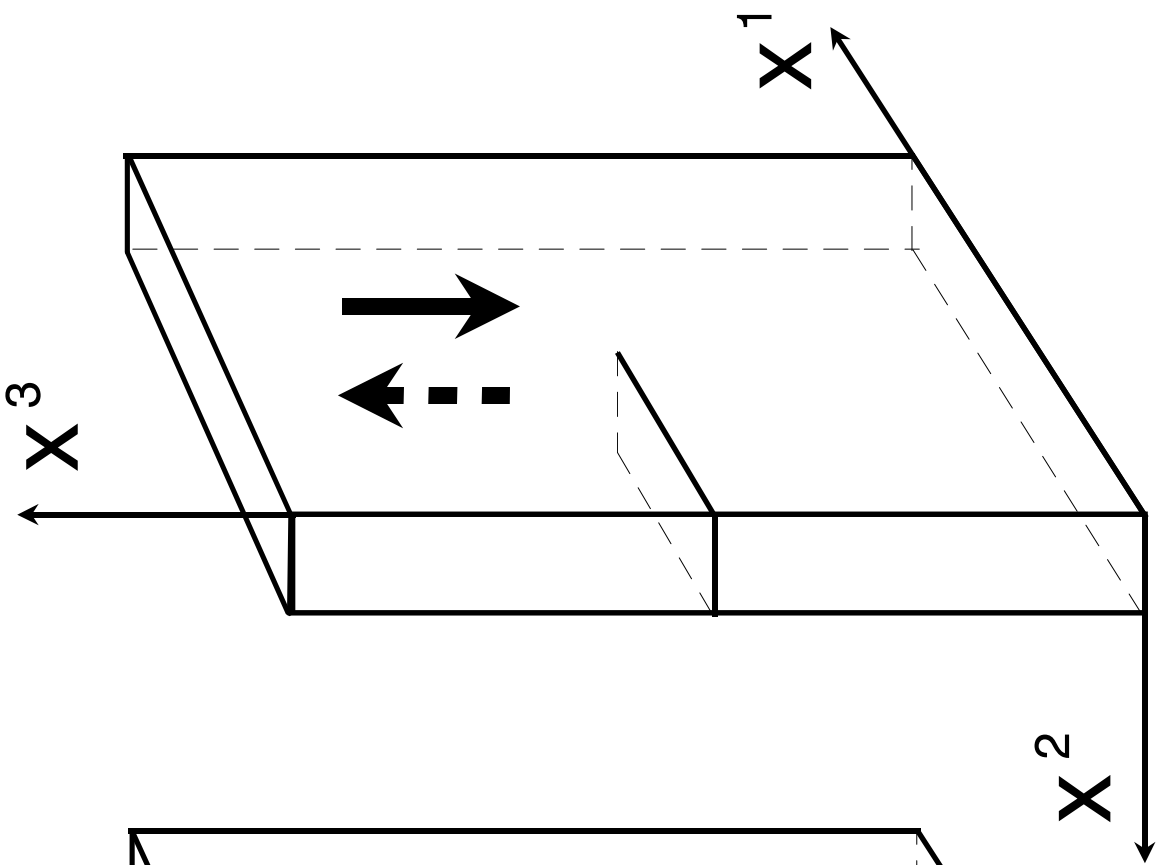

(c)